

Bulab[®] 600

Previous in-house testing showed that adding Bulab 600 to solvent-based epoxy coatings decreased cure time. Recent advances in analytical methods allowed for the testing of not only cure rate as a function of Bulab 600 concentration, but also cure rate as a function of concentration and temperature.

The base coating for these tests is displayed in the table below. The epoxy/amine ratio was adjusted to a theoretical 1:1. Bulab 600 was post added to Part A of the formulation and the concentration range was evaluated from 0–5% at 77°F, and from 0–3% for all other temperatures studied.

B36P292A Epoxy Formulation – Part A			
Item	Target weight (grams)	Actual weight (grams)	Calculated Epoxy Equivalents (Part A)
Charge the following under agitation to PT1 vessel equipped with 70 mm cowles blade			
EPOTUF [®] 38-505	354.10	354.10	
DOWANOL [™] PM	29.20	29.23	
DOWANOL [™] DPM solvent	29.20	29.20	
CYMEL [®] U-21-511	12.70	12.69	
Anti-Terra [®] -U	2.70	2.72	
Methyl isobutyl ketone (MIBK)	36.80	36.82	
Mix 15 min @ 630 rpm; add the following under agitation			
Busan [®] 11-M1	204.60	204.60	
R5098D Copperas [®] Red Iron Oxide (Dark)	153.50	153.50	
BENWOOD [™] TALC 2207	108.00	108.00	
WG [™] 325 muscovite mica	35.60	35.60	
#1 Barytes BB-2501	138.90	138.90	
Hock @ 5480 rpm (20 m/s) – 4 min, then 4300 rpm 3 min, followed by 3 min @ 3390 rpm			
Mix 10 min @ 620 rpm – Stop, raise blade, scrape sides and bottom			
Hock @ 5480 rpm (20 m/s) – 4 min, then 4300 rpm 3 min, followed by 3 min @ 3390 rpm			
Check Grind – Dirty 5.5 N.S.			
Total Part A	1105.30	1105.36	0.5058571

B36P292B Epoxy Formulation Crosslinker – Part B			
Item	Target weight (grams)	Actual weight (grams)	Calculated Amine Equivalents (Part B)
EPOTUF 37-650	65.76	65.76	
Xylene	0.70	0.70	
Total Part B	66.46	66.46	0.505856

Total Formulation	1171.76
--------------------------	----------------

EPOTUF[®] is a registered trademark of Reichhold Inc.; DOWANOL[™] is a trademark of The Dow Chemical Company (“Dow”) or an affiliated company of Dow; CYMEL[®] is a trademark of Allnex Belgium SA or its directly or indirectly affiliated Allnex Group companies; Anti-Terra[®] is a trademark of BYK-Chemie GmbH; Copperas[®] is a trademark of Rockwood Pigments NA, Inc.; BENWOOD[™] is a trademark of IMI FABI Talc Company; WG[™] is a trademark of IMERYS.

Epoxy cure as a function of Bulab® 600 addition

Initial testing showed that at 77°F gel time (indicated by the crossover point, Figure 1) and higher viscosity (Figure 2) was reached in a shorter amount of time as Bulab 600 concentration increased.

Figure 1. Loss/storage modulus curves showing gel points – 77°F


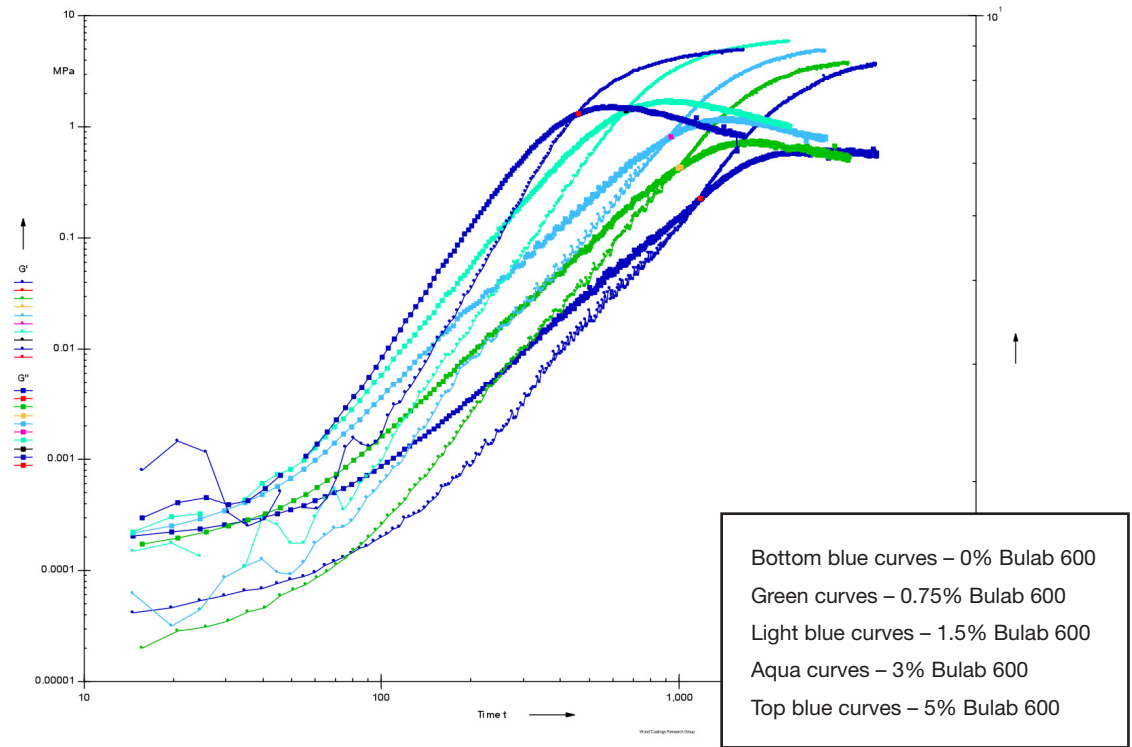


Figure 2. Complex viscosity as function of Bulab 600 – 77°F

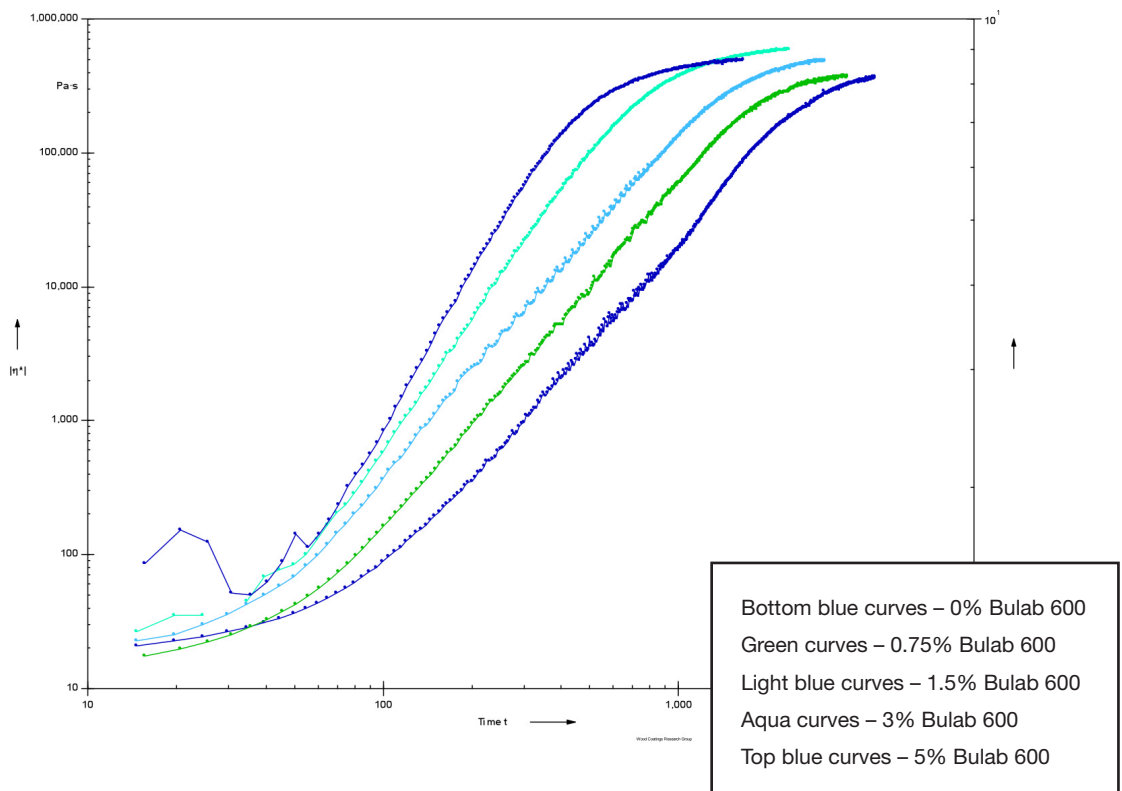

Epoxy cure as a function of Bulab[®] 600 addition and temperature

The study next determined that Bulab 600 increased the rate of solidification and crosslinking of the epoxy coating studied at each temperature investigated. Curing rate increased as the concentration of Bulab 600 increased, with the exception of an aberration observed at 0.75% at 50°F and 40°F relative to 0% Bulab 600 (Figures 3 and 4). As temperatures decrease from 77°F, the impact of Bulab 600 becomes greater, resulting in a reduced gel time relative to 0% Bulab 600. The 60°F curve shows the greatest slope while the 77°F curve the smallest slope (Figures 3 and 4).

Figure 3. Impact of temperature on gel time (G'/G'' crossover) as a function of Bulab 600 concentration

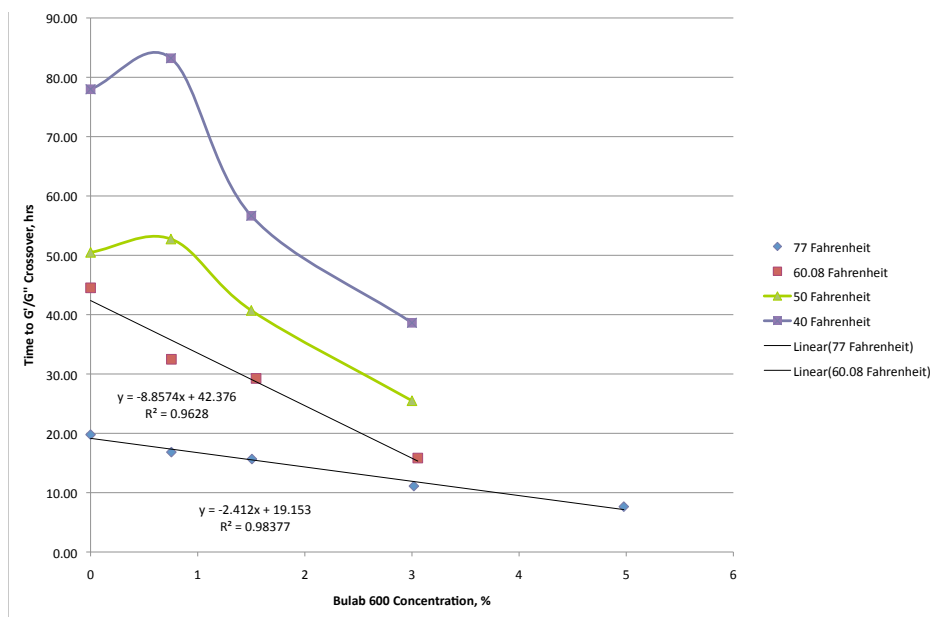


Figure 4. Impact of temperature on lineal gel time (G'/G'' crossover) as a function of Bulab 600 concentration

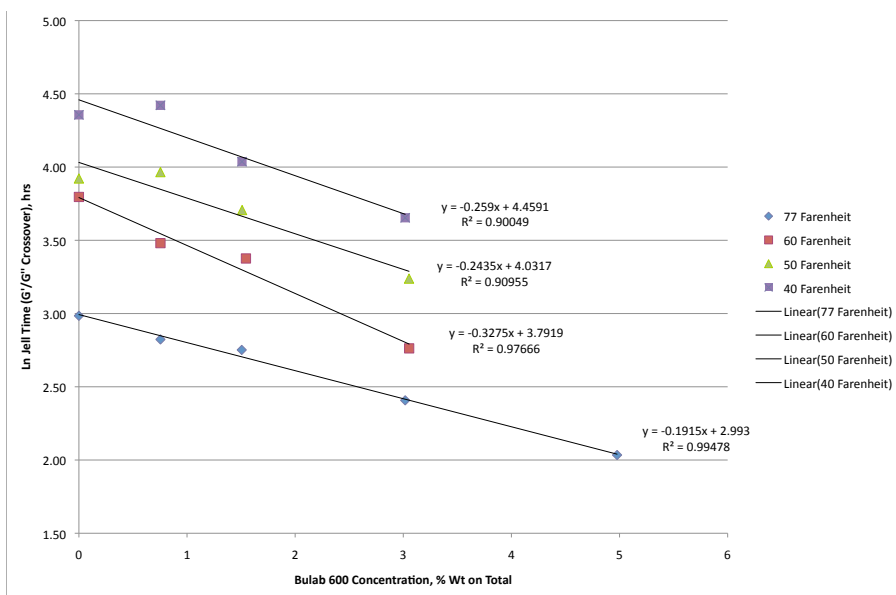


Figure 5 is an Arrhenius plot analyzing the effect of gel time as a function of temperature at a constant Bulab® 600 concentration. It is clear from the data that adding Bulab 600 dramatically improves cure of the epoxy vs. 0% Bulab 600, with 0.75% Bulab 600 showing the greatest slope for the concentrations studied.

Correlation coefficients R^2 values) are such that one may confidently predict cure-time as a function of Bulab 600 concentration and cure temperature.

Figure 5. Linear gel time vs temperature at constant Bulab 600 concentration


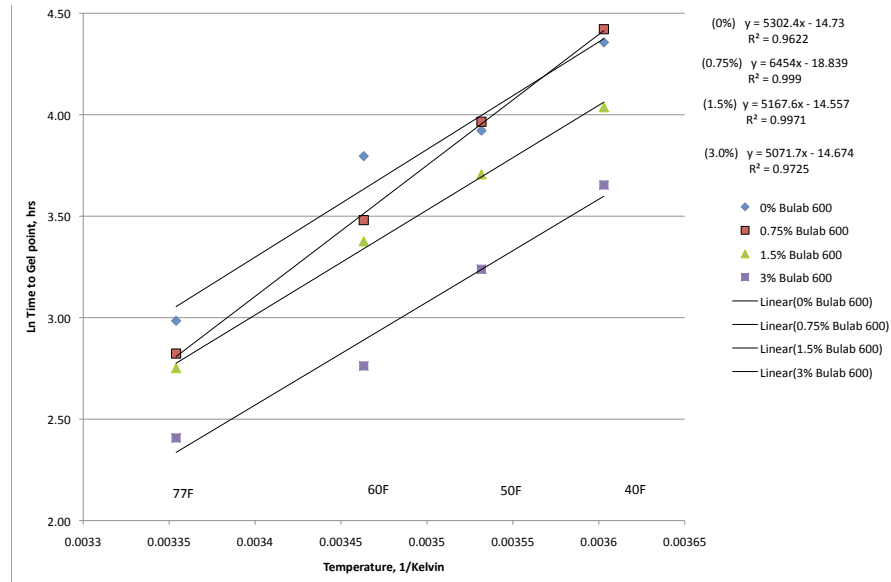


Figure 6 displays the time for the films to reach a complex viscosity of 1000 Pa·s as a function of Bulab 600 concentration and temperature. Except for the 3% Bulab concentration at 40°F, the time to reach 1000 Pa·s decreased with increasing Bulab 600 concentration at each temperature tested.

Figure 6. Impact of temperature on time $\eta^* = 1000$ Pa·s as a function of Bulab 600 concentration

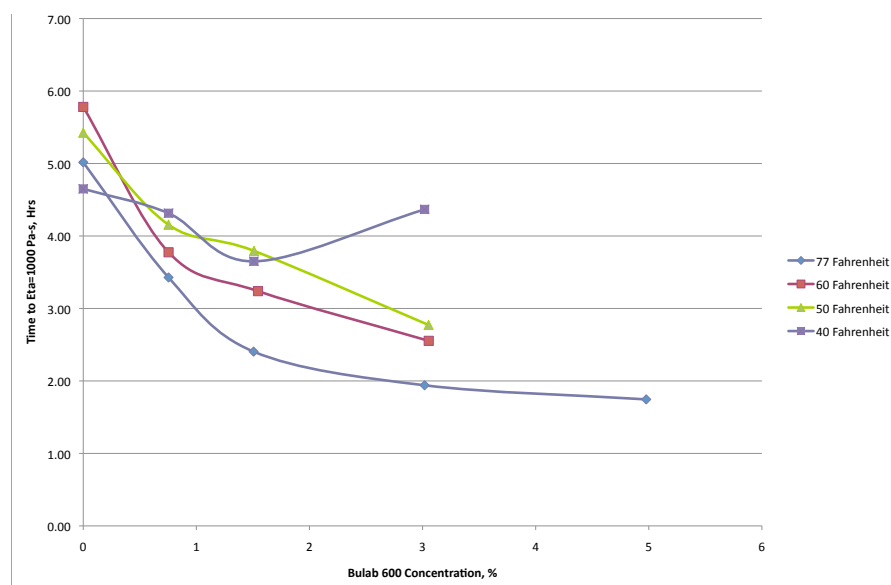

This is not an offer for sale. The product shown in this literature may not be available for sale and/or available in all geographies where Buckman is represented. The claims made may not have been approved for use in all countries. Buckman assumes no obligation or liability for the information. Please contact your Buckman sales representative for more information.

Seller warrants that this product conforms to its chemical description and is reasonably fit for the purpose referred to in the directions for use when used in accordance with the directions under normal conditions. Buyer assumes the risk of any use contrary to such directions. Seller makes no other warranty or representation of any kind, express or implied, concerning the product, including **NO IMPLIED WARRANTY OF MERCHANTABILITY OR FITNESS OF THE GOODS FOR ANY OTHER PARTICULAR PURPOSE**. No such warranties shall be implied by law and no agent of seller is authorized to alter this warranty in any way except in writing with a specific reference to this warranty. B312H (05/20)

Argentina +54 11 4701-6415; Australia +61 (2) 6923 5888; Belgium +32 9 257 92 11; Brasil +55 (19) 3864-5000; Canada +1 (877) 282-5626; Chile +56-2) 2944-1000; China +86-21) 6921-0188
 India +91) 44-2648 0220; Indonesia +62) 21-2988 8288; Korea +82) 31-416 8991; Mexico +52 (777) 329 3740; Singapore +65) 6891 9200; South Africa +27 (31) 736 8800; United States +1 (901) 278-0330

Global Headquarters at 1256 N. McLean Blvd., Memphis, TN 38108, USA